


Product Data
USG® No. 1
Pottery Plaster

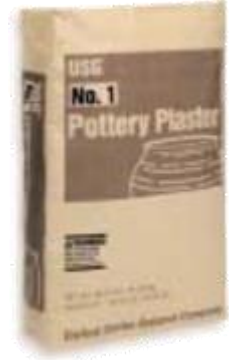

- The best material available for sanitary ware and dinnerware casting.
- Formulated for long life and reduced breakage (stronger molds).
- Available with or without thermal shock additive.


	Technical Properties	English	Metric
Use Consistency (parts of water)	70	70	
1 Hr. Compressive Strength	1,000 psi	6.8 MN/m ²	
Dry Compressive Strength	2,400 psi	16.3 MN/m ²	
Total Absorption Capacity	36%	36%	
Maximum Setting Expansion	0.210%	0.210%	
Density	Wet	99.0 lb./ft. ³	1.58 g/cm ³
	Dry	69.0 lb./ft. ³	1.10 g/cm ³
Set Time (Machine Mix) *	14-24 min.	14-24 min.	

*Other set times may also be available. Call your sales representative for more information. Hand mix times will be longer.

General Directions and Guidelines

Preparing the Mix

Use potable water at temperatures between 70° and 100° F (21° and 38° C). Since variations in slurry (the plaster and water mixture) temperature produce variations in setting time, it is important to keep both the plaster and water in a stable temperature environment prior to use. The higher the temperature of the water, the shorter the set time. See the graph below.

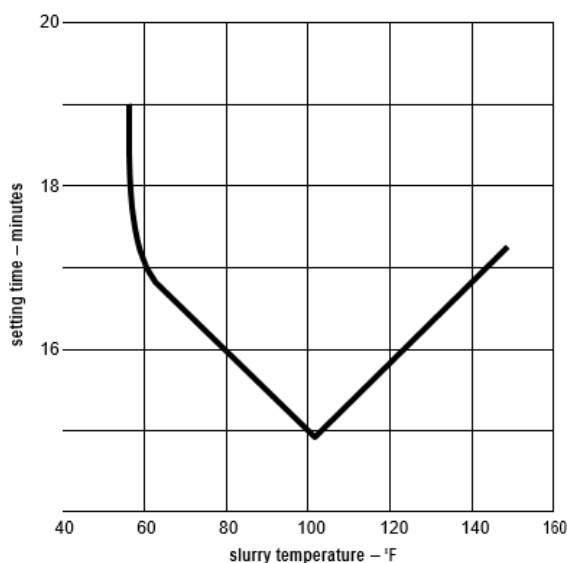



Weigh both the plaster and water for each mix. The water-to-plaster ratio is critical because it governs both the strength and the absorptive capacity of the mold.

Soaking

Sift or strew the plaster into water slowly and evenly. Do not drop handfuls of plaster directly into the water. Allow soaking for 1-2 minutes. The plaster should be fully dispersed in the water prior to mixing. Small batches require less soaking than large batches. See bulletin IG503 for specific soaking instructions.

Mixing

Mixing the plaster slurry is one of the most important steps in producing plaster molds with maximum strength, absorption, hardness, and other important properties. Mechanically mixed plasters develop uniform molds with optimal strengths. Plasters can be mechanically mixed through both batch and continuous processes. Proper blade and bucket dimensions are important for obtaining the best batch mix (see IG503 for details). Longer mixing times result in higher mold strength and shorter setting times. The relationship between mixing time and both compressive strength and setting time is shown below.

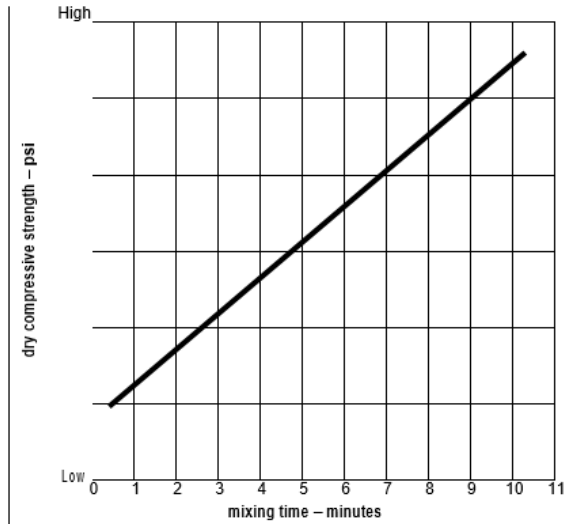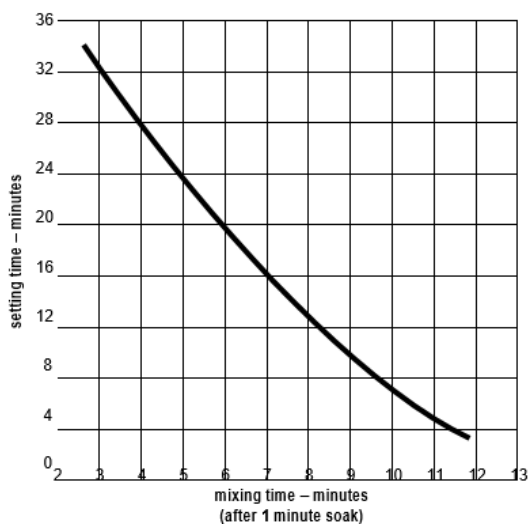

Pouring

To prevent air entrapment and provide a uniform, smooth surface, careful pouring of the plaster slurry is necessary. Agitation of the filled case mold is a further step used to prevent air at or near the mold surface. Whenever possible, the plaster slurry should be poured carefully in the deepest area so the slurry flows evenly across the surface of the case mold.



Pouring a large amount of slurry directly on the face of the case mold may result in slight densification of the plaster mold at the point where it strikes the surface of the case. This produces a hard spot, giving uneven absorption.

Drying

All pottery molds should be dried as quickly as is safely possible after manufacture so that maximum physical properties can develop. Dry to a constant weight. The best drying rooms or ovens provide (1) uniform and rapid circulation (minimum of 15-30 fps) of air with no "dead spots" having little or no air movement, (2) equal temperatures throughout the entire area, and (3) provisions for exhausting a portion of the air while replacing it with fresh air. High humidity surrounding the drying room or oven

inhibits the efficiency of the drying because the air pulled into the room is incapable of picking up much moisture from the molds.

The maximum temperature at which plaster molds are safe from calcination is 120° F (49° C). With substantial free water in the mold, higher drying temperatures can be used without difficulty. As drying progresses, the temperature must be reduced to prevent calcination. The safe drying zone is in the shaded area of graph (below, right). Before removing molds from the dryer, the temperature should approach that of the area around the dryer to prevent thermal shock.

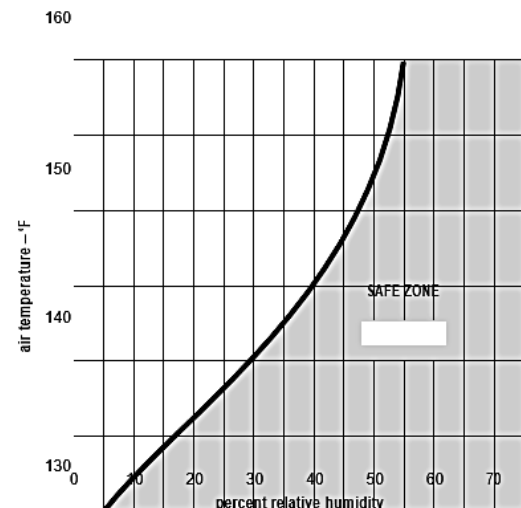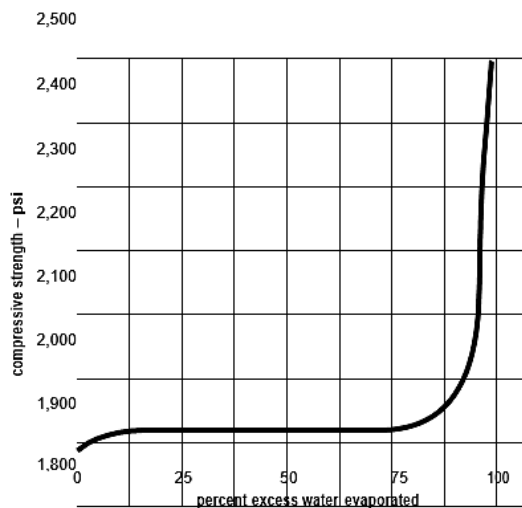

Storage

Keep in a dry, stable environment indoors. Do not stack more than 2 pallets high. Keep from drafts. Rotate stock.

Warning

When mixed with water this material hardens and becomes very hot- sometimes quickly. DO NOT attempt to make a cast enclosing any part of the body using this material. Failure to follow these instructions can cause severe burns that may require surgical removal of affected tissue amputation of limb. Dust can cause eye, skin, nose, throat, or respiratory irritation. Avoid eye contact and inhalation of dust. Wear eye protection. If eye contact occurs, flush thoroughly with water. If dusty, wear a NIOSH/MSHA-approved respirator. Use proper ventilation to reduce dust exposure. Do not ingest. If ingested call physician. Product safety information: USA (800) 507-8899.

Trademarks

The following trademarks used herein are owned by United States Gypsum or a related company: No 1 Pottery Plaster, USG.

Notice

We shall not be liable for incidental or consequential damages, directly or indirectly sustained, nor for any loss caused or by application of these goods not in accordance with current printed instruction or for other than the intended use.

Our liability is expressly limited to replacement of defective goods. Any claim shall be deemed waived unless made in writing to us within (30) days from the date it was or reasonably should have been discovered.

KEEP OUT OF REACH OF CHILDREN

Industrial Gypsum Division
 125 South Franklin Street
 Chicago, IL 60606-4678
 A Subsidiary of USG Corporation
 ©1999, United States Gypsum Company

800 487.4431
 312.606.5380 www.usg.com/ig
 E-mail: industrialgypsum@usg.com

IG1381/5-99 Printed in U.S.A.

